

 <b>CPC</b> <small>CONSOLIDATED PRESSURE CONTROL</small>	CPC ENGINEERING SPECIFICATION		
	SECTION SOP	Doc. No. CES-26-128	
	ISSUE "A"	REV "0"	
	DATE: 18-02-2024	Page 1 of 7	

**GENERAL REQUIREMENT FOR FORGED OR WROUGHT MATERIALS FOR**  
**GASKET & PSL L 2,3 & 4**

Rev	Reason of Change	Date	Made By	Reviewed By	Approved By	Status
0	Initial Release	18-02-2024	PK	USR	JG	Released



 <b>CPC</b> <small>CONSOLIDATED PRESSURE CONTROL</small>	CPC ENGINEERING SPECIFICATION	
	SECTION SOP	Doc. No. CES-26-128
	ISSUE "A"	REV "0"
	DATE: 18-02-2024	Page 2 of 7

## GENERAL REQUIREMENT FOR FORGED OR WROUGHT MATERIALS

### FOR GASKET & PSL L 2,3 & 4

#### 1.0 PURPOSE

This document is to define the minimum requirements for processing and certification, for forged or wrought materials.

#### 2.0 SCOPE

This specification establishes material requirements for forgings or wrought materials for PSL level 1, 2, 3 & 4. It shall be used in conjunction with specific material specifications (MS) or approved vendor supplied material specifications. This specific Material Specification may amend or modify the requirements of this specification.

#### 3.0 REFERENCE

The latest effective editions of the following specifications are incorporated as reference and form a part of these specifications.

API 6A - Specification for wellhead and Tree Equipment API

ASTM A-370 or ISO 6892-1 or IS: 1608: 2005 - Standard Test methods and Definitions for Mechanical Testing of Steel products.

ASTM E-10 or ISO 6506- Standard Test Method and Brinell Hardness of Metallic Materials.

ASTM E-18 or ISO 6508- Standard Test Methods for Rockwell Hardness and Rockwell superficial hardness of Metallic Materials.

CES 26-109 Charpy Impact Test requirement

CES 26-110 Specification for General Requirements of Heat Treatment of Alloy Steels for Use in Well Head. Christmas Tree, Manifold and Related Equipment

CWI-27-011 Visual Examination

#### 4.0 RESPONSIBILITY

The Engineering Manager is responsible for the preparation and controls the material specifications. Quality Control Manager supported by quality management is responsible for the implementation of the material requirements.



 <b>CPC</b> <small>CONSOLIDATED PRESSURE CONTROL</small>	CPC ENGINEERING SPECIFICATION	
	SECTION SOP	Doc. No. CES-26-128
	ISSUE "A"	REV "0"
	DATE: 18-02-2024	Page 3 of 7

## 5.0 DEFINITIONS

**5.1 Heat Treat Lot A.** Batch Furnace-Material Placed on loading or carry devices and moved as a batch through one heat-treat cycle.

**B.** Continuous Furnace-Group of pieces of material with the same nominal size that is moved sequentially through the heat treatment process using the same process parameter.

## PROCEDURAL REQUIREMENTS

### 6.1 MELTING PRACTICE

- 6.1.1 Steel products shall be made by the electric furnace or basic oxygen furnace process. Additional may be performed by ladle refining, vacuum degassing, vacuum arc re-melting (VAR), electro slag re-melting (ESR), or argon oxygen decarburization (AOD).
- 6.1.2 Nickel base alloy primary melting method shall be vacuum induction or electric arc furnace or induction furnace with or without argon oxygen decarburization (AOD). Secondary processing shall be electro slag re-melting (ESR) or vacuum arc re-melting (VAR).

### 6.2 MILL PRACTICE


Product supplied to this specification shall be free from defects which would detrimentally affect serviceability. Such defects include, but are not limited to, cracks, laps, flakes, fissures, slag, porosity, and rolled-in scale.

### 6.3 HOT WORKING PRACTICE

- 6.3.1 The material shall be of pressure vessel quality and shall be formed using a hot Working practice, which produce a wrought structure throughout. Hot working practice shall be documented.
- 6.3.2 Hot working practice shall produce a minimum reduction ratio of 3:1. When requirements dictate a 4:1 or greater reduction ratio, the reduction ratio shall be specified on the applicable part.
- 6.3.3 The QTC hot working ratios that are equal to or less than those used in processing the production part(s) it qualifies. The total hot working ratio for the QTC shall not exceed the total hot working ratio of the part(s) it qualifies.

### 6.4 MATERIAL QUALIFICATION

- 6.4.1 Minimum tensile, and if required, impact properties tests shall be performed on a qualification test coupon (QTC). Test specimens shall be removed from the QTC after the final QTC heat treatment cycle, and shall be from the same melt, or re-melt ingot (s) as the production material/ part (s).
- 6.4.2 The properties of the QTC shall represent the properties of the material comprising the production material/part(s) it qualifies. A QTC may only qualify material/part(s) produced from the same heat. The hot working ratio used on or less than that used on production material/part(s).



CPC ENGINEERING SPECIFICATION	
SECTION SOP	Doc. No. CES-26-128
ISSUE "A"	REV "0"
DATE: 18-02-2024	Page 4 of 7

**6.4.3** When the QTC is obtained by trepanning or using a sacrificial production material/part(s), it may only qualify production material/part(s) having the same or smaller ER as that used to obtain the QTC.

Note: The equivalent Round (ER) of the QTC shall be equal to or exceed that of the material/part(s) being heat-treated. The ER of the material/part(s) shall be determined using the actual dimensions of the material/part(s) in the as heat-treated condition per the calculation method specified in FIG 1. The QTC shall be a minimum of 7" long for a standard specimen. The maximum ER required shall be 5" (4" x 4" QTC) unless otherwise specified by the specific part requirements. Tensile specimens shall be removed from the QTC such that their longitudinal centerline axis is wholly within the center core 1/4 T envelopes for a solid QTC or within 1/8 inch of the mid-thickness of the thickest section of a hollow QTC (refer to FIG 1). The impact specimens shall be removed such that the notch is within the 1/4 T envelopes. For QTCs larger than the ER or greater than 4" x 4", the test specimens need not be removed from a location farther from the QTC surface than would be required if the specified QTC were used.

**6.4.4** Test specimens shall be removed from the QTC such that the tensile specimen gauge length and Charpy V-Notch root are the least 1/4 T from the ends of the QTC. For Charpy Impact Requirement refer CES 26-109.

**6.4.5** When sacrificial production material/part(s) is used as a QTC, the test specimens shall be removed from a section of the part meeting the size requirement for a QTC for that production part. For all flanges of diameter 8" and above sacrificial part shall be used as QTC.

**6.4.6** Tensile test shall be conducted per the procedures of ASTM A-370 or ISO 6892-1 or IS 1608:2005. Tensile test shall be performed at room temperature between 4 °C and 50 °C (between 40 °F and 120 °F) unless an elevated temperature is specified. Standard size 0.505 Inch diameter tensile specimen or a sub size 0.252-inch diameter specimen as referred in ASTM-370 shall only be used. A minimum of one test shall be performed. The results shall satisfy the applicable specific Material Specification. If the results of the tensile test are not satisfactory, two additional tensile tests may be performed. The result of each of these tests shall satisfy the applicable requirements.

**6.4.7** The heat treated QTC shall be checked for hardness per ASTM-E-10 or E-18 or ISO 6506 or ISO 6508 as applicable per spec requirement. A minimum of one hardness test shall be performed on the QTC. For API 16A products hardness testing shall be performed in accordance with ISO 6892 or ISO 6506-1 as appropriate.

**6.4.8** For material heat treated in a continuous furnace, the QTC shall consist of a sacrificial production part or a prolongation removed from production part. The sacrificial production part or prolongation QTC shall qualify only production parts having an identical shape and size. The QTC shall qualify only materials and parts produced from the same heat and heat treat lot. For continuous furnaces, a heat treat lot is defined as a group of pieces of material with the same nominal size that is run through the furnace sequentially at the same zone temperatures, travel speed, and other parameters.



 <b>CPC</b> <small>CONSOLIDATED PRESSURE CONTROL</small>	CPC ENGINEERING SPECIFICATION	
	SECTION SOP	Doc. No. CES-26-128
	ISSUE "A"	REV "0"
	DATE: 18-02-2024	Page 5 of 7

A minimum of one QTC shall be provided for each of material. Tensile and impact tests shall be conducted on the QTC in accordance with paragraphs 5.2 through 5.7. A hardness traverse shall be conducted on a cross-section from QTC, with Brinell hardness readings taken at the surface, the 1/4 diameter location, and the center of the bar. In addition to the testing required on the QTC, each bar shall be individually hardness checked. Brinell hardness measurements shall be taken on the surface at two or more locations.

## 6.5 HEAT TREATMENT


- 6.5.1 Material/part(s) and QTC shall be heat treated per the process cycle listed in the specific Material Spec. Equipment used for heat treatment shall have a temperature uniformity of  $\pm 25$  °F or 14 °C ( $\pm 15$  °F OR 8 °C for tempering furnaces) inside the heating chamber. Material/part(s) shall be loaded in the furnace such that the heat treat response of all material/part(S) will be uniform.
- 6.5.2 The quenching media and agitation should be of sufficient capacity for the furnace load.
- 6.5.3 Material/part (s) shall be traceable to and marked with the heat treat lot (heat treat batch) identification.
- 6.5.4 When the QTC is not heat treated as part of the same heat treatment lot as the material/part(s) it qualifies, the Austenizing (Or solutionizing) temperature for the QTC shall be within 25 °F (14 °C) of those for the material/part(s). The tempering temperature of the material/part(s) shall not be lower than 25 °F (14 °C) below that of the QTC. The upper limit shall be no higher than that permitted by the specific MS. The cycle time at each temperature shall not exceed that for the material/part (s).

## 6.6 INSPECTION

Material shall be inspected for injurious imperfections as listed in the following:

- 6.6.1 Material provided in the rough machined condition shall not exceed 250 AA in surface roughnesses in the machined areas, and shall be free of burrs or injurious imperfections;
- 6.6.2 Material shall have workmanlike finish and shall be free of internal forging burst or hydrogen ilakes.
- 6.6.3 Surface imperfections such as laps, seams, folds, tear silver or mechanical marks, abrasion or pits need not be removed unless they infringe on the minimum wall thickness of the material or extend to a depth greater than 1/6 inch.




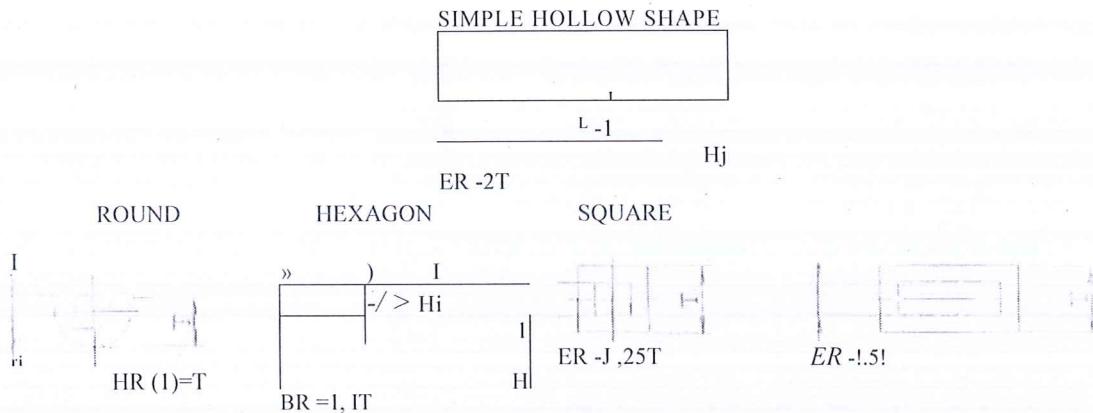

a) SIMPLE GEOMETRIC EQUIVALENT ROUND SECTIONS/SHAPE SHAVING

### LENGTH L

**b) GENERAL, FLANGED BODIES FOR COMPLEX-SHAPED WELLHEAD COMPONENTS**



c) KEEL BLOCK CONFIGURATION, ER=2,3R

- a) When  $L$  is less than  $T$ , consider section as a plate of thickness area inside of dashed lines is  $1/4T$  envelope for test specimen removal.
- b) When  $L$  is less than  $D$ , consider as a plate of  $T$  thickness.
- c) On multi flanged components,  $T$  shall be the thickness of the thickest flange.
- d) Where  $T$  is the thickness when the component is heat treated as in T (2), use the larger of the two indicated dimensions.
- e) Bodies with screwed and open ends.

0 Envelope for test specimen removal



 <b>CPC</b> <small>CONSOLIDATED PRESSURE CONTROL</small>	CPC ENGINEERING SPECIFICATION	
	SECTION SOP	Doc. No. CES-26-128
	ISSUE "A"	REV "0"
	DATE: 18-02-2024	Page 7 of 7

NOTE: When all internal and external surfaces during heat treatment are within 13mm (1/2 in) Of the final surfaces, ER=1-1/4T when all internal and external surfaces during heat treatment are not with in 13mm (1/2 in) of the final surface, then ER=2T.

## 6.7 VISUAL EXAMINATION

- 6.7.1 Sampling to be performed in accordance with ISO 2859-1:1999, level II, 2.5 AQL for O-rings and 1.5 AQL for other seals.
- 6.7.2 Each piece of the sample to be visually inspected according to Procedure for Visual Examination of steel castings / Forgings / Wrought Material and Welded Joints (CWI-27-011)
- 6.7.3 If inspection methods produce rejections less than allowed in sampling, the batch will be accepted.

