


SES 26 - 776

 Sara Sae	SARA SAE ENGINEERING SPECIFICATION		
	Section: SES 26 – 776		
	Issue: "A"		Rev No.: "0"
	Eff. Date: 24-07-2014		Page: 1 of 3

MATERIAL SPECIFICATION
FLUOROCARBON (VITON) ELASTOMER

Rev	Reason of Change	Date	Made By	Reviewed By	Approved By	Status
0		24-07-2014	KKM	USR	KKD	Released

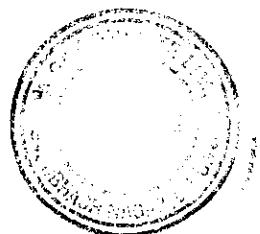

 Sara Sae	SARA SAE ENGINEERING SPECIFICATION		
	Section: SES 26 – 776		
	Issue: "A"	Rev No.: "0"	
	Eff. Date: 24-07-2014	Page:	2 of 3

MATERIAL SPECIFICATION
FLUOROCARBON (VITON) ELASTOMER

1.0 PURPOSE

- 1.1 It is the purpose of material specification to list in a concise form of the material requirements for Fluorocarbon Elastomers to be used in Sour Service at temperature from – 15° F to +400 °F. (-26°C to +205°C)
- 1.2 This material specification is intended to aid the purchasing department in procuring and the vendor in supplying a product which meets the needs of its intended use, and the quality control department in the inspection and release of incoming material.

2.0 SCOPE

- 2.1 This material specification covers sour services, medium- high CAN, Sulphur cure compounds recommended for service with petroleum oils and fuels, water, and glycols.

3.0 Pressure Limits:


Static:	20,000 PSI, Liquid / 10,000 PSI, Gas
Dynamic:	10,000 PSI, Liquid / 5,000 PSI, Gas

4.0 Chemical composition: The standard formulas for Viton Rubber compounds are as in ASTM D-1418.

Polymer Type	Vinylidenefluoride/hexafluoropropylene/tetrafluoroethylene Terpolymer
Trade Designation	VF2/HFP/TFE
ASTM D1418 designation	FKM
Trade names	Viton GF

4.1 Chemical Compatibility:

H ₂ O (Water)	Yes
CH ₄ (Methane)	Yes
N ₂ (Nitrogen Gas)	Yes
CO ₂ (Carbon Dioxide)	Yes
H ₂ S (Hydrogen Sulfide)	Yes
Chlorides	Yes
HCl (Hydrochloric Acid)	Yes, Cold
H ₂ SO ₄ (Sulfuric Acid)	Yes, Cold
H ₂ CO ₃ (Carbonic Acid)	Yes, Cold
O ₂ (Oxygen)	Yes



 Sara Sae	SARA SAE ENGINEERING SPECIFICATION		
	Section: SES 26 - 776		
	Issue: "A"	Rev No.: "0"	
	Eff. Date: 24-07-2014	Page:	3 of 3

5.0 Physical Properties: The ASTM standard specifications to determine the physicals are given below.

PROPERTIES	RANGE
HARDNESS (ASTM D-2240) Shore "A" Durometer	70 \pm 5 Pts.
TENSILE STRENGTH (ASTM D-412) Min.	2,000 PSI
ELONGATION (ASTM D-412) Min.	150%
100% Modules (ASTM D-412) Min.	700 PSI
SPECIFIC GRAVITY (ASTM D-792, A)	1.15 \pm 0.05
COMPRESSION SET (ASTM D-395, B) Method 'B' Max. 22 HRS @ 212° F	15

6.0 Fluid Immersion Data

70 Hours @ 212° F, IRM 903 Oil, ASTM D-471

VOLUME CHANGE, %, Max.	10	ASTM D471
HARDNESS CHANGE, %, Max.	56	
TENSILE STRENGTH CHANGE %, Max.	25	
ELONGATION CHANGE %, Max.	20	

